



Experimental analysis of mechanical, tribological, morphological of AA5022 based nano-scaled vanadium and tin-reinforced composites

Velu Chandran ^{a,*}, Lenin Nagarajan ^b, Kalpathi Mathivanan ^c, Thomas Manvel Raj ^d

a. Department of Automobile Engineering, Velammal Engineering College, Chennai, India.

b. Department of Mechanical Engineering, SRM TRP Engineering College, Trichy, India.

c. Department of Mechanical Engineering, SV College of Engineering, Tirupati, India.

d. Department of Mechanical Engineering, Hindustan University, Chennai, Tamil Nadu, India.

* Corresponding author: chandran1979mt@gmail.com (V. Chandran)

Received 9 February 2023; Received in revised form 13 June 2024; Accepted 17 November 2024

Keywords

AA5022;
 Hybrid Composites;
 Vanadium;
 Tin;
 Tribology.

Abstract

This research work investigates the mechanical and dry friction wear behavior of the AA5022 matrix reinforced with nano-scaled particles. In this work, nano-scaled vanadium and tin were blended with an aluminum matrix, and the aluminum composite samples with different weight percentages of nano-scaled vanadium and tin in the 0–10 wt% range were fabricated through a muffle furnace and stir-casting techniques. The obtained results reveal that the tensile strength and microhardness progressively increase with nano-scaled vanadium and tin addition in the aluminum matrix up to 6 wt% of each. The wear loss and wear rate gradually decrease in the same samples. The internal structure of nano-scaled vanadium and tin-reinforced hybrid aluminum composite samples was examined by scanning electron microscopy, which revealed that, sample C (6 wt% of nano-scaled vanadium and tin particles) microstructure appeared uniform distribution and was intensively dispersed in the aluminum matrix. The pure AA5022 was also studied to compare the mechanical and tribological properties. Sample C improved by 39% in tensile strength and improved by 22% in microhardness. Moreover, hybrid aluminum composite samples showed improved wear-resistant characteristics, which can be used for various tribological applications, especially in electric automotive and modern aerospace.

1. Introduction

In the over few years, the universal need for minimum cost, higher performance, and superior quality materials has been carried out on composite materials by numerous researchers. The operating low-cost, low wear performance and high strength-to-weight ratio play a vital role in modern aerospace, automobile, and other related modern industries. Aluminum is the most extensively used metal matrix composite in the modern scenario. It is mainly because of the distinctive characteristics of low density, good mechanical properties, low electrical resistance, good machinability, and excellent corrosion resistance. Modern engineering applications have a lot of more current demands; hybrid aluminum composites have the great potential to satisfy their demands. Al 6061-Albite-Graphite reinforced hybrid

composites show good tribological behavior, which emerges as an attractive alternative hybrid composite material for high-end applications [1]. The prediction of wear properties performance is of supreme significance in the present industrial scenario, to evaluate the life span of friction-based components in advance to avoid huge financial losses acquired on account of wear [2]. The hybrid aluminum composites density improves with reinforcements like TiC, SiC, and etc. The addition of reinforcements such as fly ash, mica, and rice husk reduces the density of the hybrid composites [3]. The reinforcement particle size, shape, type, and distribution in the matrix leads to internal microstructure and the volume fraction of reinforcement, which determines the composite surface and wear characteristics [4]. The

To cite this article:

V. Chandran, L. Nagarajan, K. Mathivanan, T. Manvel Raj "Experimental analysis of mechanical, tribological, morphological of AA5022 based nano-scaled vanadium and tin-reinforced composites", *Scientia Iranica* (2025) 32(14): 7548. <https://doi.org/10.24200/sci.2024.61905.7548>

aluminum composite performance is mostly reliant on choosing the right combination of reinforcing particles and processing parameters [5]. The inclusion of B₄C particle reinforcement leads to decreases in the wear rate and improves the wear resistance performance of the aluminum hybrid composites [6]. The mechanical and mechanical behavior of hybrid composites improved with combination of fly ash and SiC particles [7]. The wear performance of hybrid composites decreased with the increase of the graphite inclusion in the aluminum matrix to 1.5 wt%, and hence graphite is not supported by the wear properties [8]. The mechanical properties of the aluminum matrix improve with the addition of SiC, B₄C, and alumina particles [9]. The wear rate is not affected notably with load and sliding velocity, but reinforcement particle size significantly affects the wear properties. [10,11]. The addition of micro and nano reinforcement particles in the aluminum matrix has improved the mechanical and wear performance [12]. The superior strength of aluminum or its combination is not all around investigated. Even though, a few studies have resulted in a significant increment in mechanical and wear characteristics of hybrid aluminum composites and therefore, more investigation is required in this spot of further development in hybrid aluminum matrix [13]. The uniform dispersion of nano-sized metal particles in the hybrid aluminum matrix plays a vital role due to their strong tendency for the agglomeration and good interface bonding, which resulted for enhancing the characterization of the hybrid aluminum matrix [14]. The inclusion of reinforcement in the form of discontinuous or irregular reinforcement particles of boron carbide and zirconium carbide particles lead to an improving the characterization of aluminum metal matrix composites [15]. Nowadays, most vehicle body structures are employed with lightweight and high-strength nano metal matrix composites, and the most important properties of light-weight and high-strength are simultaneously demanded in most modern applications [16]. The improved mechanical and wear properties of the multi-component aluminum matrix can be accomplished by the inclusion of low refractory and melting metal particles. To facilitate superior characterization, metal nano-scaled particles are added into the aluminum matrix and further investigations are needed for the determination of the best possible content of nano-scaled particles in the aluminum matrix with an improved set of mechanical and wear properties [17]. The hybrid metal matrix composites are attractive materials for applications of mechanical, multi-functional, medical, energy and industrial and thus, it can be considered for the development of second generation of composite materials [18]. The vanadium carbide particle reinforced metal matrix composites were developed due to spontaneous growth of vanadium carbide during solidification, and uniformly distributed vanadium carbide in metal matrix, which results in good metallurgical bonding [19]. The aluminum composites reinforced with fly ash in different sizes of particles showed suitability in numerous applications like highway signs, automobile components, and industrial products. The minimum particle sized reinforced composites are found to be enhanced mechanical performance [20,21]. The nano-sized particle quantity and its dispersion in the matrix are dependent on the development of composites in better characteristics [22]. The abrasive wear accounts for 50% of wear in the most components of

industrial applications [23]. The wear performance of any material depends on input parameters such as load applied, sliding distance, and sliding velocity, property of material, machine characteristics, and environmental conditions of the machining operations [24]. The nano-sized particles reinforced aluminum composites significantly enhance the wear characteristics of matrix [25]. The material surface damages induce a change in the geometry of the components, which increased the surface crack propagation and tends to increase the tribological rate [26]. The improvement in the mechanical, and tribological performance of different aluminum matrix depends on the percentage of reinforcement particles, number of reinforced particles and ranges of particle sizes in the fabricated aluminum composites [27]. The wear rate is greatly affected by the volume fraction of reinforced particles in the aluminum matrix, and the relationship between reinforced particle grain size, volume fraction, and sliding distance is important for the wear properties of the hybrid aluminum composites [28]. Investigation of Al/20Cu/10Mg reinforced composites exhibited significant improvements in mechanical properties. They are composed of two different metals with good solubility, which provide better interfacial bonding by forming intermetallic, whereas dissolved particles help to achieve dispersion strengthening in composite structures [29]. The reinforced particle shape, size, and volume fraction, manufacturing process, and the interface between the matrix and the reinforcement phases of the composites affect the mechanical and wear behavior of metal matrix composites [30].

Consequently, mechanical and wear behavior of different metal matrix composites has been studied in the literature. However, to our knowledge, effect of vanadium (hard particle) and tin (soft particle) content on mechanical and wear behaviors of AA5022 hybrid composites has not been investigated. The main aim of present work is to fabricate hybrid aluminum composites using reinforcement of nano-scaled vanadium and tin particles to analyze the mechanical and dry sliding wear performances. In this research, we analyzed the effects of different proportions of nano-scaled vanadium and tin reinforcements on the density, microstructure, mechanical (tensile strength, hardness, and % of elongation), and wear properties of an AA5022 matrix. Based on the results obtained, the developed hybrid aluminum composites could be used as an innovative standpoint in enhancing the performance of composites in electric automotive and aerospace applications.

2. EXPERIMENTAL

2.1. Materials

AA5022 is an aluminum alloy, and it has high strength, high formability panel material, and soft coat baking reduced proof stress. It is also capable of being improved by utilizing adding the proper reinforcing materials. Vanadium (V) is a shiny grey, malleable, ductile transition soft metal and its density of vanadium is 2.56 g/cm³. Vanadium nanoparticles provide ultra-high surface area (particle size range: 40-60 nm). Tin (Sn) is a silvery-white color hard metal and its density of tin 4.67 g/cm³. Tin nanoparticles provide good surface area (particle size range: 30-60 nm). This research

Table 1. Chemical composition of AA5022 alloy (wt%).

Si	Fe	Cu	Mg	Mn	Cr	Al
0.25	0.4	0.2-0.5	0.2	3.5 – 4.9	0.1	Blance

Table 2. The formulation of hybrid aluminum composites with nanoscaled vanadium and tin.

S. No.	Sample code	Aluminum AA 5022 (wt%)	Nano-scaled vanadium (wt%)	Nano-scaled tin (wt%)
1	O	100	-	-
2	A	96	2	2
3	B	92	4	4
4	C	88	6	6
5	D	84	8	8
6	E	80	10	10

work is intent to study the performance of mechanical and tribological behavior of aluminum matrix with incorporation of both soft and hard nano-scaled particles. The different proportions of nano-scaled vanadium and tin particles reinforced with aluminum alloy were used for this research work. The ingots of AA5022 were provided by Navistar Steel Corporation Limited, Mumbai, India with its chemical distribution of AA5022 is tabulated in Tables 1 and 2 represented the formulation table, which is used to fabricate the hybrid aluminum composites.

2.2 Hybrid composites preparation

Stir casting is the most preferable process or method for the fabrication of hybrid composite materials. First, clean the plunger, furnace, mold, and stirrer using carbide paste to avoid settling molten metal when they contact it. Place the furnace and plunger into the stir casting machine. The reinforced nano-scaled materials (V and Sn) having different material nature and meting temperatures and hence dissimilar methods and time periods were used for vanadium and tin, respectively. Place the mold at the bottom of the setup in the correct position. Switch on the setup, adjust the initial temperature to 85°C and place the base material, AA5022, into the furnace and allow the temperature to rise further by closing the furnace. At the same time, preheat the vanadium in the muffle furnace at a temperature of about 600°C. After attaining a definite temperature, take the vanadium carefully from the muffle furnace and put that into the stir casting furnace. Wait till the materials change into molten form at about 720°C to 780°C. Then add tin carefully at the last of the fabrication process due to tin material has a lower melting temperature (232°C). Fix the stirrer carefully

into the motor, and after fixing, turn on the motor switch and allow a rotating stirrer by giving low speed, making the AA5022 vanadium tin blended properly in a molten metal form. Then, turn off the motor switch, after 3-5 minutes turn on the pneumatic switch, which makes the plunger move backward and allows the molten metal to fall into the mold kept at the bottom. The cylindrical tube mold was used to fabricate the hybrid aluminum composites in this research work. After some time, take out the mold, loosen the bolts and then take the upper part of the mold and remove the material. The aluminum alloy with various proportions of nano-scaled vanadium and tin (hybrid aluminum composites) were fabricated based on the above formulation table. Then, the samples were prepared according to the mechanical and tribological testing as per ASTM standards. The machinery used for the fabrication process and fabricated hybrid aluminum composites are shown in Figure 1.

2.3. Testing of density of material

The density of the aluminum hybrid composites was computed using both the geometric method and the Archimedes technique (with distilled water at 25°C as the submersion liquid). The relative density of the hybrid aluminum composite sample was calculated using the rule of mixture blends, which utilizes the theoretical bulk thickness values of all the aluminum hybrid composite samples.

2.4. Testing of mechanical characterization

The fabricated hybrid aluminum composite samples were used for the testing of various mechanical characterizations like tensile properties and hardness. The tensile tests were performed at room temperature on a UTM at the cross-head speeds of 600 mm/min. The dumb-bell specimen was prepared according to ASTM D-412. Hardness was tested using BHN with test standards as per the ASTM E10-14, uses tungsten carbide indenter. The 100 N load was applied for 15 seconds with indentation speed of 40 mm/s. The indentation image displayed by the computer, which was processed through dedicated software to compute the Brinell hardness numbers. Five iterations of the test were conducted, and the mean was noted.

2.5. Testing of tribological characterization

Pin-on-disc test apparatus was used to determine the dry sliding wear characteristics of the aluminum hybrid composite samples as per the ASTM G99-95 standards with Model TR 20-LE, Ducom. The wear test is conducted by taking the parameters like sliding velocity, load, and sliding distance. The initial weight of the sample is to be properly cleaned and measured using the electronic weighing machine. The specimens were machined to a pin size of

**Figure 1.** Fabrication process and hybrid composites.

10 × 25 mm. Wear testing is used to test the wear resistance of solid materials. The wear rate unit is (mm³/Nm).

2.6. Testing of morphological characterization

The morphology testing was carried out in Scanning Electron Microscope model TESCAN VEGA3, which produces images of a sample and the electrons interact with atoms, producing various signals that contain information about the samples of surface topography and composition of aluminum hybrid composites.

3. Results and discussion

3.1. Analysis of mechanical properties

The density, micro hardness, and tensile properties were used to assess the mechanical characterization of the hybrid aluminum composites. In this study, 5 samples (S1, S2, S3, S4, S5) for each fabricated aluminum hybrid composites were subjected to testing and the average value was recorded, which has been shown in Table 3 along with vanadium and tin materials.

The density of hybrid composites is improved with the incorporation of nano-scaled vanadium and tin particles. Figure 2 shows that the density of the hybrid aluminum matrix slightly increases when the reinforcement particles increase which is due to the agglomeration of dual nanoparticles. In other words, the density increased with increasing the reinforcement dual materials and the hybrid composites showed improved density due to its higher densi-

fication ability and more agglomeration. It is obvious that there is not much difference among the pure aluminum alloy and reinforcement particles and it confirms the preparation suitability of hybrid composites for stir casting processes. Moreover, theoretical and experimental density of different hybrid aluminum composite samples are recorded in Table 4.

The micro hardness is improved upon incorporating nano-scaled vanadium and tin particles in the aluminum matrix. Figure 3 shows the hardness progressively increased with the addition of nano-scaled vanadium and tin particles in the aluminum matrix. It was due to the addition of reinforced nano-scaled particles acting as an encumbrance to dislocation motion, further due to satisfactory bonding between the aluminum matrix and reinforced material.

In addition to more V and Sn in matrix, it is observed that micro hardness slightly decreases and is due to the formation of void nucleation by increasing more reinforced particles and it led to a decrease in micro hardness. Also, it can be concluded that the agglomeration of particles in the matrix with a high percentage of reinforcement particles, which results in higher porosity due to the formation of voids and pits, leads to decrease the micro hardness [31].

The tensile stress-strain curves of the hybrid nano composites increase linearly with the increase in dual reinforcement with compared to pure aluminum matrix as shown in Figure 4. It was due to the reduction in grain size, uniform distribution and amount of soft and hard reinforcing particles into the matrix. The maximum tensile strength

Table 3. The mechanical properties of hybrid aluminum composites.

Type of testing	Vanadium	Tin	Sample O	Sample A	Sample B	Sample C	Sample D	Sample E
Micro hardness in HBW	36± 0.02	51 ± 0.03	49 ± 0.34	54 ± 0.19	55 ± 0.22	60± 0.42	58 ± 0.13	57± 0.18
Tensile strength in MPa	110.3± 0.04	67.63 ± 0.02	106.32 ± 0.16	118.82 ± 0.30	128.43 ± 0.38	145.36 ± 0.46	131.94 ± 0.26	127.47 ± 0.33
Elongation at break in %	2.36± 0.03	1.64 ± 0.04	1.86 ± 0.14	1.96 ± 0.13	6.96 ± 0.18	8.70 ± 0.24	2.32 ± 0.10	1.46 ± 0.18

Table 4. Theoretical and experimental density of different hybrid aluminum composites.

Sample code	Theoretical density (g/cm ³)	Experimental density (g/cm ³)
Sample O	2.5903	2.5709±0.0003
Sample A	2.6406	2.6303±0.0010
Sample B	2.6901	2.6708±0.0009
Sample C	2.7003	2.6802±0.0012
Sample D	2.7202	2.7001±0.0011
Sample E	2.7004	2.6803±0.0015

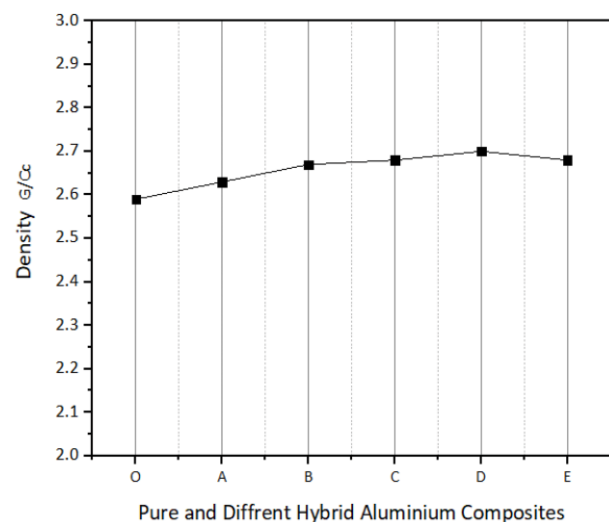


Figure 2. Density of all hybrid composites filled with V&Sn.

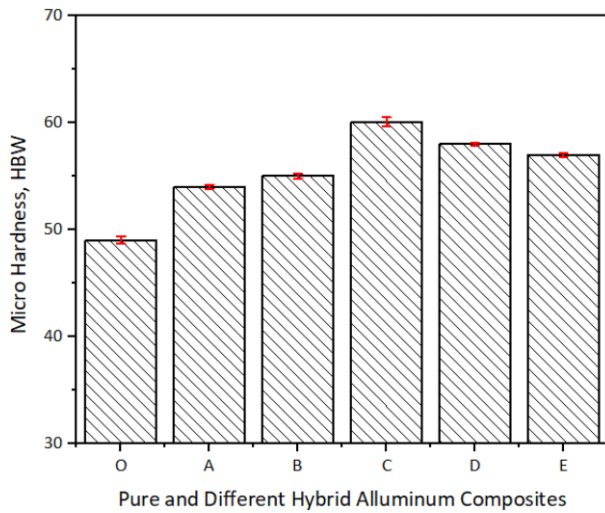


Figure 3. Micro Hardness of all hybrid composites filled with V&Sn.

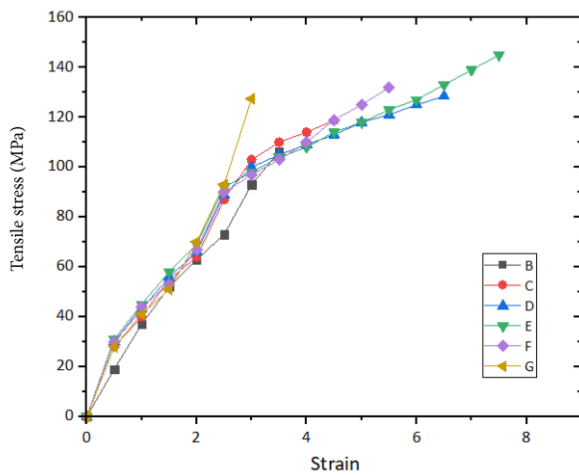


Figure 4. Tensile stress-strain curves for different hybrid nano-scaled composites and AA5022.

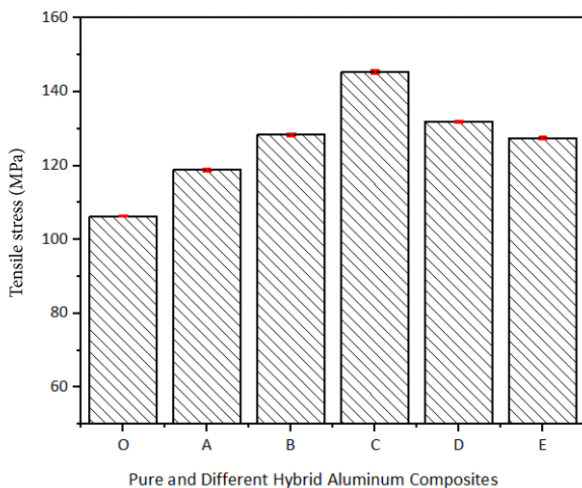


Figure 5. Tensile strength of hybrid composites filled with V&Sn.

(145.36 MPa) of the sample C nano-scaled composite was approximately 39% more than the tensile strength (106.32 MPa) of the AA5022 sample.

Figure 5 shows the tensile strength gradually increased with V and Sn loading in hybrid aluminum matrix up to 6 wt%, which was due to uniform distribution of the V and Sn

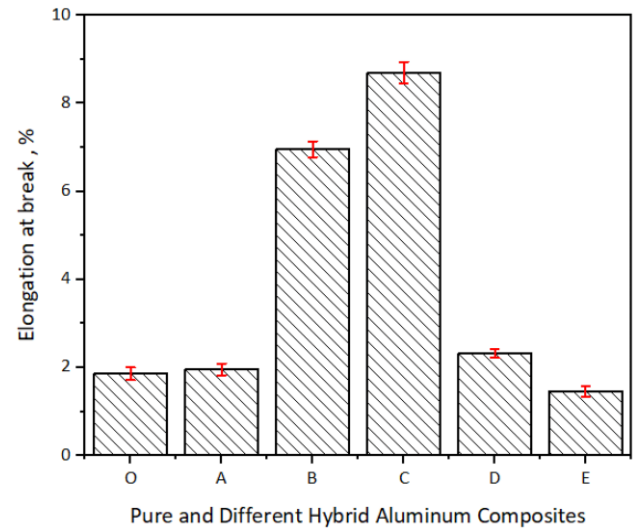


Figure 6. Elongation at break of all hybrid composites filled with V&Sn.

reinforcements and the more efficient load transfer from the matrix to the reinforcement in the metal matrix due to the two different reinforcement materials and these reinforced particles build much strength to matrix by offering additional resistance to tensile stresses [32,33]. The addition of more reinforced particles into the matrix, loosens its tensile strength, which was due to a more dual particles agglomeration, and in homogeneous distribution of reinforcing particles, which causes of strain fields in the matrix.

The elongation at break is enhanced with the addition of nano-scaled vanadium and tin particles. Figure 6 shows the elongation at break steeply increases with V and Sn loading in hybrid aluminum matrix up to 6 wt%, and it shows the addition of these nano reinforced particles enhances the ductility levels of the composites. It was due to the homogeneous dispersion of V and Sn in the aluminum matrix, and the thermal mismatch between the matrix and the reinforced particles, which reasons for superior dislocation density in the matrix [34]. With the further inclusion of more nano-scaled reinforced particles, elongation of the hybrid aluminum composites drastically reduced due to an increase in the weight percentage of reinforcements and the formation of void nucleation because of this, elongation at break decreases [35].

3.2 Analysis of wear properties

The wear loss and wear rate were used to assess the tribological characterization of the hybrid aluminum composites. In this study, five samples are subjected to all these testing and the corresponding values were recorded in Table 5.

The abrasion loss of aluminum hybrid composite material was assessed in terms of wear rate in different parameters like load variation, sliding velocity, and sliding distances. The loads (10 N, 20 N, 30 N, 40 N, and 50 N), Sliding distances (500 m, 1000 m, 1500 m, 2000 m, and 2500 m), and Sliding velocity (1.2 m/s, 2.4 m/s, 3.6 m/s, 4.8 m/s and 6.0 m/s) are different parameters to undergone for the tribological testing to determine the wear characterization of hybrid aluminum composites as indicated in Table 6.

Table 5. The tribological properties of hybrid aluminum composites.

Type of testing	Sample O	Sample A	Sample B	Sample C	Sample D	Sample E
Initial weight in g/ms	5.50	5.42	5.84	6.74	6.68	6.59
Final weight in g/ms	5.15	5.16	5.58	6.56	6.43	6.33
Wear loss in g/ms	0.35	0.25	0.26	0.17	0.25	0.26
Wear rate in mm ³ /N-m	6.33	4.62	4.48	2.62	3.73	3.94

Table 6. Wear rate in different parameters (Load, sliding distance, and sliding velocity).

Load		Sample O	Sample A	Sample B	Sample C	Sample D	Sample E
		Wear rate (mm ³ /N-m)					
Test-1	10 N	6.33	4.62	4.48	2.62	3.73	3.94
Test-2	20 N	7.14	5.83	5.64	4.74	4.82	4.96
Test-3	30 N	7.94	6.22	6.78	5.11	5.21	5.54
Test-4	40 N	8.34	7.12	7.48	6.62	6.73	6.94
Test-5	50 N	8.84	7.62	7.98	6.94	6.85	7.18
Sliding distance		Wear rate (mm ³ /N-m)					
Test-1	500 m	7.11	5.41	5.28	4.48	4.52	4.71
Test-2	1000 m	7.91	6.43	6.32	5.52	5.61	5.74
Test-3	1500 m	8.71	7.02	7.48	5.99	6.01	6.31
Test-4	2000 m	9.11	8.14	8.12	7.12	7.46	7.74
Test-5	2500 m	9.66	8.53	8.51	7.78	7.80	8.21
Sliding velocity		Wear rate (mm ³ /N-m)					
Test-1	1.2 m/s	6.01	4.12	3.93	2.11	3.22	3.45
Test-2	2.4 m/s	6.64	5.31	5.14	3.13	4.29	4.45
Test-3	3.6 m/s	7.34	5.77	6.11	4.53	4.76	5.04
Test-4	4.8 m/s	7.85	6.66	7.00	5.11	6.22	6.47
Test-5	6.0 m/s	8.32	7.11	7.45	6.44	6.52	6.83

Figure 7 shows that the wear rate gradually decreased with the addition of nano vanadium and tin particles loading in aluminum matrix up to 6 wt% in all load variations. As load increases, the abrasion loss also increases and relates to the coefficient of wear rate is increased with an increase in load conditions. It is observed that the average abrasion loss of the hybrid composite is relatively low compared to pure alloy.

The homogeneous dispersion of nanoparticles in the matrix led to improving the Interfacial reaction and proper distribution among the V and Sn in the matrix. The inclusion of additional reinforcements in the matrix loses their interfacial reaction and improper distribution and hence

loosens the wear characteristics of aluminum hybrid composites.

Figure 8 shows the wear rate of hybrid aluminum composites at different sliding distance conditions, in which incorporation of V and Sn particles in the matrix, improves the wear resistance of hybrid aluminum composites up to 6 wt%. Incorporation of more same nanoparticles that lose their interfacial reaction and loosen their wear resistances and hence wear rate increases. Figure 9 shows the wear rate of hybrid aluminum composites at different sliding velocities. It results improve the wear resistance of hybrid aluminum composites up to 6 wt%, which is due to uniform dispersion and the good interfacial reaction of nanoparticles

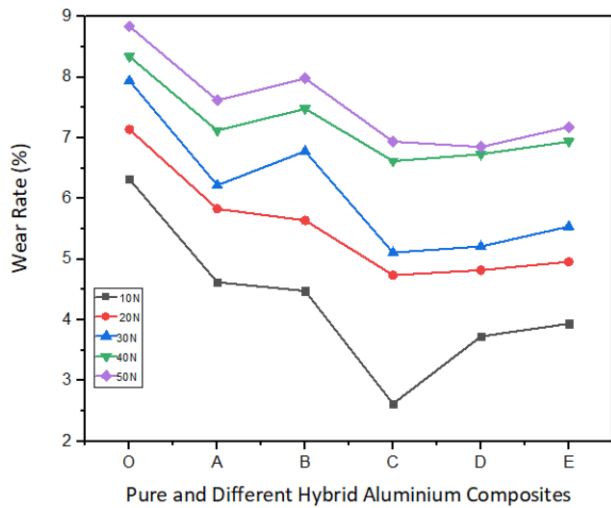


Figure 7. Wear rate of pure and hybrid composites at load variation.

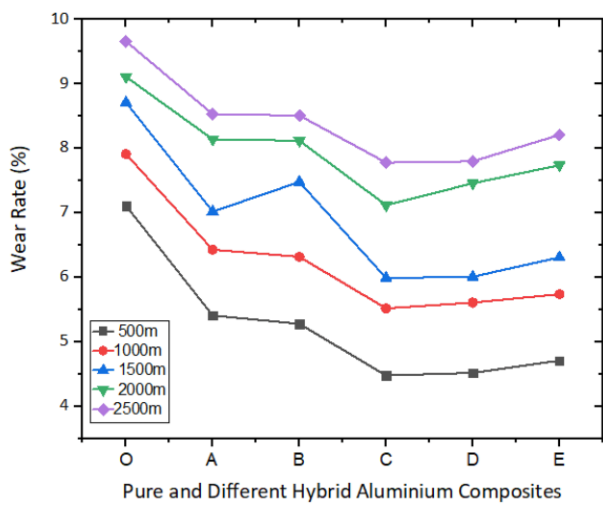


Figure 8. Wear rate of pure and hybrid composites at sliding distance variation.

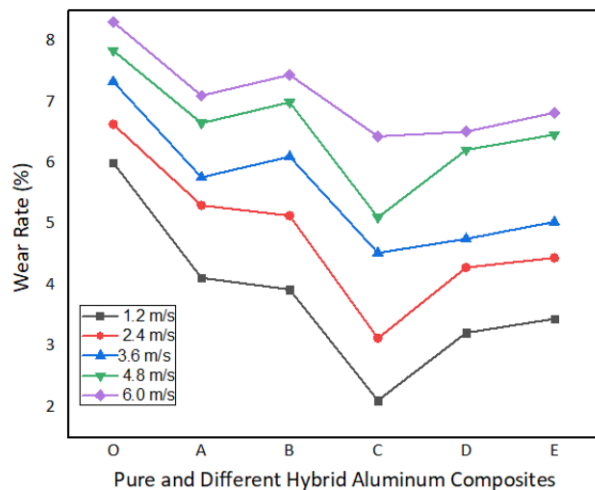


Figure 9. Wear rate of pure and hybrid composites at sliding velocity variation.

in the matrix. The incorporation of more same particles lose their wear resistance and hence wear rate increases. With the increase of sliding velocity in all specimens, the wear rate tends to increase since the reinforced particles unevenly spread on the surface, which leads to unable to protect the composite surfaces, and hence wear rate increases.

3.3 Analysis of micrographs

Figure 10 shows the wear surface of samples of pure alloy and all hybrid aluminum composites containing nano-scaled vanadium and tin in different proportions. Sample a facilitated a good interfacial reaction between V and Sn in the aluminum matrix and it observed that significant dimple pattern and small wear debris, which leads to improved mechanical and wear properties compared to pure alloy (sample O). The accumulation of the more nano-scaled particles in the matrix (sample B) which leads to presence of some wear debris on the worn surfaces. Sample C facilitates better interfacial reaction and bonding between V and Sn particles in the aluminum matrix, and it is observed that settled dimple pattern and also less wear debris and there are no shallow grooves, which leads to improving the tensile and wear properties.

Samples D and E facilitated improper interfacial reaction and no uniform distribution of reinforced particles are detached from the worn surfaces during the wear tests. And it is observed that more minor wear debris and shallow grooves, which correlates to the micro-crack and micro-void formation in hybrid aluminum composites [36]. It led to a decrease in the tensile and wear properties of aluminum hybrid composite, similar wear results were obtained from the previous study on the tribological properties. Hence, the all-morphology samples were analyzed and it reveals that 6 wt% of nano-scaled vanadium and tin particles dispersed intensively in the AA5022 matrix (sample C), which will show the better mechanical and tribological performance of the hybrid aluminum composites.

4. Conclusion

This research aims to improve the mechanical and tribological properties of hybrid aluminum composites. The following conclusions arrived for the samples made of different compositions of nano-scaled vanadium and tin particles in the aluminum matrix, and the mechanical, tribological characterization and morphological analysis were carried out for all fabricated hybrid composites.

1. The density of hybrid composites increases with nano-scaled vanadium and tin particles, which indicates that there are not many differences between the pure aluminum alloy and hybrid aluminum composites, and it confirms the preparation suitability of hybrid composites in the stir casting process;
2. The micro hardness gradually increases with the incorporation of nano-scaled vanadium and tin particles in the aluminum matrix to 6 wt%. The addition of more same particles loosens the micro hardness. Moreover, sample C of micro hardness improved approximately by 22% when compared with pure alloy;
3. The tensile strength gradually increases with the loading of nano scaled vanadium and tin particles in the aluminum matrix to 6 wt%. The addition of more same particles loosens the tensile strength. Moreover, tensile strength of sample C improved by 39% more than when compared with pure alloy;
4. The elongation at break gradually increases with nano scaled vanadium and tin particles in the aluminum matrix till 6 wt%. The addition of more same particles loosens the elongation;

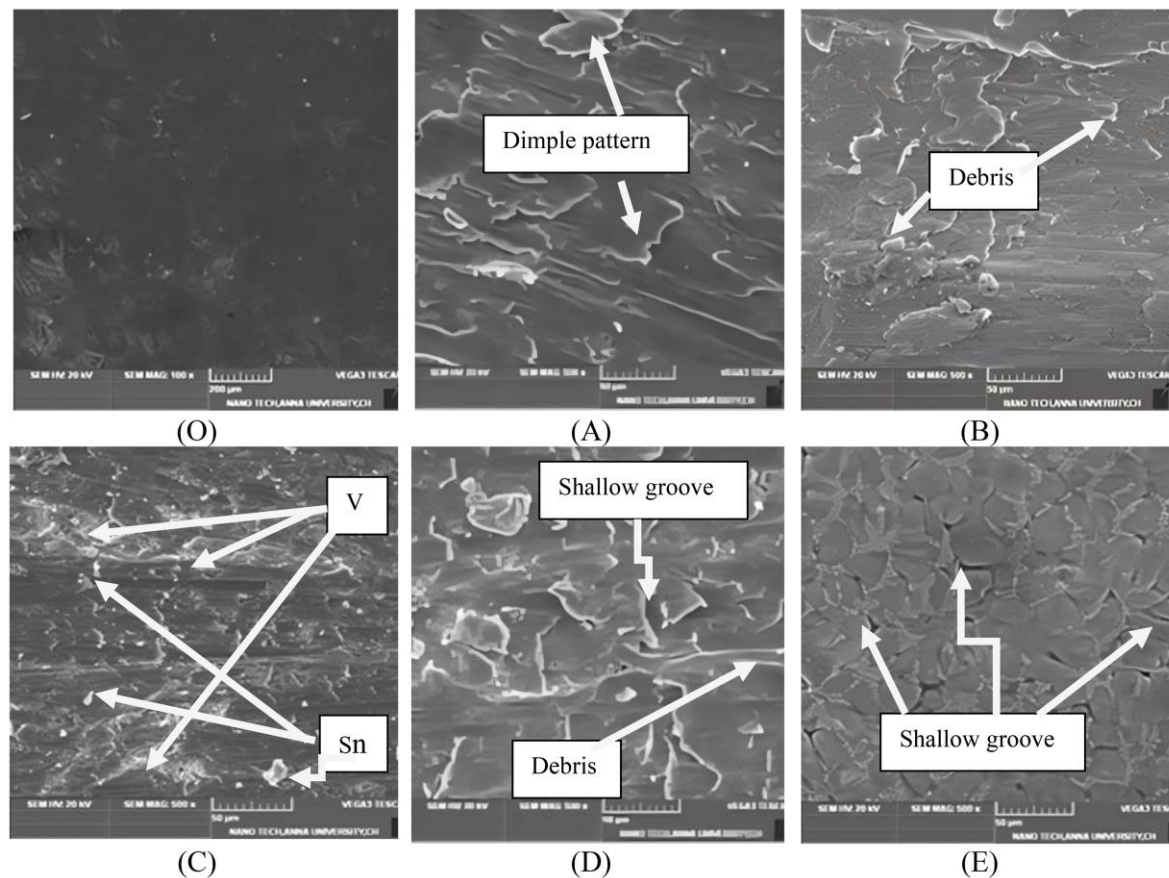


Figure 10. The SEM images of the worn surfaces of all hybrid composites containing nano-scaled V&Sn particles.

5. The wear loss and wear rate gradually reduce with the incorporation of nano-scaled vanadium and tin particles in the matrix of all hybrid composites fabricated when compared to pure alloy.

6. Tribological properties reveals that, the wear rate of nano-scaled vanadium and tin particles reinforced hybrid composites showed less value when compared to pure alloy with various parameters like load, sliding distance, and sliding velocity.

7. The samples' morphology revealed that 6 wt% of nano-scaled vanadium and tin particles dispersed intensively in the AA5022 matrix, which will improve the mechanical and tribological performance of the hybrid aluminum composites.

8. Moreover, this research work concludes that hybrid aluminum composites containing 6 wt% V and 6 wt% Sn nano-scaled particles suitable for applications where mechanical and wear performances are more important, especially in the electric modern automotive and aerospace applications.

Funding

This research did not receive any specific grant from funding agencies in the public, commercial, or not-for profit sectors.

Conflicts of interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Authors contribution statement

First author: Data curation; Formal analysis; Writing - original draft; Writing - review & editing

Second author: Conceptualization; Data curation

Third author: Investigation; Methodology; Project administration

Fourth author: Software Supervision; Validation; Visualization

References

1. Madhukar, P., Selvaraj, N., Rao, C.S.P., et al. "Manufacturing of aluminium nano hybrid composites: a state of review", *Mater. Sci Eng.*, **149**(2), pp. 1-12 (2016).
<https://doi.org/10.1088/1757-899X/149/1/012114>
2. Bodunrin, M.O., Alaneme, K.K., and Chown, L.H. "Aluminum matrix hybrid composites: a review of reinforcement philosophies; mechanical, corrosion and tribological characteristics", *J. Mater. Res. & Tech.*, **4**(4), pp. 434-445 (2015).
<https://doi.org/10.1016/j.jmrt.2015.05.003>
3. Siddesh Kumar, N.G., Ravindranath, V.M., and Shiva Shankar, G.S. "Mechanical and wear behavior of aluminium metal matrix hybrid composites", *Proc. Mater. Sci.*, **5**, pp. 908-917 (2014).
<https://doi.org/10.1016/j.mspro.2014.07.378>
4. Raja Selvam, J.D., Robinson Smart, D.S., and Dinaharan,

- I. "Synthesis and characterization of Al6061-fly ash-sic_p composites by stir casting and compocasting methods", *Ener. Proc.*, **34**(3), pp. 637-646 (2013).
<https://doi.org/10.1016/j.egypro.2013.06.795>
5. Kenneth, K.A. and Kazeem, O.S. "Microstructural characteristics, mechanical and wear behavior of aluminum matrix hybrid composites reinforced with alumina, rice husk ash and graphite", *Eng. Sci. and Tech. Int. J.*, **18**(3), pp. 416-422 (2015).
<https://doi.org/10.1016/j.jestech.2015.02.003>
6. Himanshu, K., Merb, K.K., Sandeep Kumar, A., et al. "A review on mechanical and tribological behaviors of stir cast aluminum matrix composites", *Proc. Mater. Sci.*, **6**, pp. 1951-1960 (2014).
<https://doi.org/10.1016/j.mspro.2014.07.229>
7. Michael, O.B. and Kenneth, K., and Lesley, H.C. "Aluminium matrix hybrid composites: a review of reinforcement philosophies; mechanical, corrosion and tribological characteristics", *J. Mater. Res. Tech.*, **4**(4), pp. 434-445 (2015).
<https://doi.org/10.1016/j.jmrt.2015.05.003>
8. Anand, N. and Senthil Kumaran, S. "Development and influence of tribomechanical properties on magnesium-based hybrid metal matrix composites-A review", *Mater. Res. Exps.*, **7**(3), pp. 1-14 (2018).
<https://doi.org/10.1088/2053-1591/ab7d08>
9. Nadeem, F. and Kaushik, K. "Mechanical and tribological behaviour of nano scaled silicon carbide reinforced aluminium composites", *J. Exp. Nano Sci.*, **13**, pp. S1-S13 (2018).
<https://doi.org/10.1080/17458080.2018.1431846>
10. Sardar, S., Karmakar, S.K., Das, D., et al. "High stress abrasive wear characteristics of Al7075 alloy and 7075/Al₂O₃ composite", *Measurement*, **127**(5), pp. 42-62 (2018).
<https://doi.org/10.1016/j.measurement.2018.05.090>
11. Vivudh, G.B. and Mishra, R.K. "Tribological characteristics of AA7075 composites reinforced with rice husk ash and carbonized eggshells", *J. Mater. Des. App.*, **235**(11), pp. 214-232 (2021).
<https://doi.org/10.1177/14644207211025810>
12. Girimurugan, R., Pugazhenth, R., Suresh, T., et al. "Prediction of mechanical properties of hybrid aluminium composites", *Mater Today Proc.*, **39**(1), pp. 712-716 (2021).
<https://doi.org/10.1016/j.matpr.2020.09.302>
13. Minlin, Z., Dafa, J., Hongjun, Z., et al. "Fabrication of nano particulate reinforced metal matrix composites by laser cladding", *J. Laser App.*, **26**(2), pp. 2007-2018 (2014).
<https://doi.org/10.2351/1.4867735>
14. Rajmanickam, T. and Marimuthu, K. "Experimental investigation of mechanical and tribological properties of Al6061-ZrC-B₄C hybrid composites", *Transac. Canadi Soc. Mech Engg.*, **45**(3), pp. 429-443 (2020).
<https://doi.org/10.1139/tcsme-2020-0137>
15. Massoud, M., Wenwu, X., Ashish, K., et al. "Advanced metal matrix nano composites", *Metals.*, **9**(1), pp. 330-341 (2019).
<https://doi.org/10.3390/met9030330>
16. Grigoriev, N., Mironov, A., Ekaterina, K., et al. "Enhancement of the mechanical and tribological properties of aluminum-based alloys fabricated by SPS and alloyed with Mo and Cr", *Metals*, **11**(12), 1900 (2021).
<https://doi.org/10.3390/met11121900>
17. Megahed, M., Attia, M.A., Abdelhameed, M., et al. "Tribological characterization of hybrid metal matrix composites processed by powder metallurgy", *Acta Metall. Sin.*, **30**, pp. 781-790 (2017).
<https://doi.org/10.1007/s40195-017-0568-5>
18. Zhang, Y., Lai, R., Chen, Q., et al. "The correlation analysis of microstructure and tribological characteristics of in situ VC_p reinforced iron-based composite", *Materials*, **14**(15), 4343 (2021).
<https://doi.org/10.3390/ma14154343>
19. Jaineswar, N., Sankar, N.D., Anup, C., et al. "Wear analysis of aluminum-fly ash hybrid composites", *Mater. Today: Proc.*, **33**(8), pp. 5461-5466 (2020).
<https://doi.org/10.1016/j.matpr.2020.03.259>
20. Abushanab, W., Moustafa, E., Ghandourahc, E., et al. "The effect of different fly ash and vanadium carbide contents on the various properties of hypereutectic Al-Si alloys-based hybrid nano composites", *Silicon*, **14**, pp. 5367-5377 (2022).
<https://doi.org/10.1007/s12633-021-01284-0>
21. Veereshkumar, G.B., Pramodet, R., Ramu, P., et al. "Investigation of the tribological characteristics of aluminum 6061-reinforced titanium carbide metal matrix composites", *Nanomaterials*, **11**(11), 3039 (2021).
<https://doi.org/10.3390/nano11113039>
22. Massimo, L., Alberta, A., Giulio, M., et al. "Understanding friction and wear behavior at the nano-scale of aluminum matrix composites produced by laser powder bed fusion", *Adv. Eng. Mater.*, **22**(3), pp. 1-12 (2020).
<https://doi.org/10.1002/adem.201900815>
23. Sharma, O.P. and Meena, A. "Study of mechanical properties and wear behavior of aluminum 6061 matrix composites reinforced with hematite and titania", *Mater. Today, Proc.*, **44**(4), pp. 5028-5036 (2021).
<https://doi.org/10.1016/j.matpr.2021.01.131>
24. Suresh, R., Jothi, A.G., Siddeshkumar, N.G., et al. "Investigation on dry sliding wear behavior of AA5083/nano-AlO metal matrix composites", *Revista de Metalurgia.*, **58**(1), pp. 1-22 (2022).
<https://doi.org/10.3989/revmetalm.213>
25. Zakeri, A., Bahmani, E., Ramezani, A., et al. "A review

- on the enhancement of mechanical and tribological properties of MCrAlY coatings reinforced by dispersed micro and nanoparticles”, *Energies*, **15**(5), 1914 (2022). <https://doi.org/10.3390/en15051914>
26. Pranavi, U., Venkateshwar Reddy, P., Venukumar, S., et al. “Evaluation of mechanical and wear properties of Al 5059/B₄C/Al₂O₃ hybrid metal matrix composites”, *J. Compos. Sci.*, **6**(3), 86 (2022). <https://doi.org/10.3390/jcs6030086>
 27. Priyanka, C., Parimala, P., Vishwanath, K.N., et al. “Optimization on tribological behaviour of AA7178 nano titanium diboride hybrid composites employing taguchi techniques”, *J. Nanometer.*, **2022**, 1619923 (2022). <https://doi.org/10.1155/2022/1619923>
 28. Canakci, A., Ozkaya, S., Erdemir, F., et al. “Effects of Fe–Al intermetallic compounds on the wear and corrosion performances of AA2024/316L SS metal/metal composites”, *J. Alls. Comps.* **845**, 156236 (2020). <https://doi.org/10.1016/j.jallcom.2020.156236>
 29. Onur, G., Mulim, C., Ramazan, D., et al. “Novel ZA27/B₄C/graphite hybrid nanocomposite-bearing materials with enhanced wear and corrosion resistance”, *Metal. Materi. Transac.*, **51**(1), pp. 4632-4646 (2020). <https://doi.org/10.1007/s11661-020-05863-5>
 30. Yalcin, E.D., Canakci, A., Erdemir, F., et al. “Enhancement of wear and corrosion resistance of ZA27/nano grapheme composites produced by Powder Metallurgy”. *Arabian J. Sci. Eng.*, **44**, pp. 1437-1445 (2019). <https://doi.org/10.1007/s13369-018-3582-7>
 31. Karabacak, A.H., Canakci, A., Erdemir, F., et al. “Corrosion and mechanical properties of novel AA2024 matrix hybrid nano composites reinforced with B₄C and SiC particles”, *Silicon*, **14**, pp. 8567-8579 (2022). <https://doi.org/10.1007/s12633-021-01582-7>
 32. Zihni, A.C., Abdullah, H.K., Metin, K., et al. “The effect of machining processes on the physical and surface characteristics of AA2024-B₄C-SiC hybrid nano composites fabricated by hot pressing method”, *J. Compos. Mater.*, **55**(19), pp. 2657-2671 (2021). <https://doi.org/10.1177/0021998321996419>
 33. Yunus, M. and Alfattani, R. “Assessment of mechanical and tribological behavior of AA6061 reinforced with B₄C and Gr hybrid metal matrix composites”, *Coatings*, **13**(9), 1653 (2023). <https://doi.org/10.3390/coatings13091653>
 34. Nirala, A., Soren, S., Kumar, N., et al. “Micro-mechanical and tribological behavior of Al/SiC/B₄C/CNT hybrid nano composite”, *Sci. Rep*, **13**, 13147 (2023). <https://doi.org/10.1038/s41598-023-39713-2>
 35. Natrayan, L., Raviteja, S., Prabu, P., et al. “Statistical experiment analysis of wear and mechanical behaviour of abaca/sisal fiber-based hybrid composites under liquid nitrogen environment”, *Polym. Compos. Mater.*, **10**, pp. 1-12 (2023). <https://doi.org/10.3389/fmats.2023.1218047>
 36. Garg, H.K., Sharma, S., Kumar, R., et al. “Mechanical, tribological, and morphological properties of SiC and Gr reinforced Al-0.7Fe-0.6Si-0.375Cr-0.25Zn based stir-casted hybrid metal matrix composites for automotive applications: Fabrication and characterizations”, *J. Mat. Res. and Tech.*, **28**(3), pp. 3267-3285 (2024). <https://doi.org/10.1016/j.jmrt.2023.12.171>

Biographies

Velu Chandran is an Associate Professor of the Automobile Engineering Department, Velammal Engineering College. He is having 18 years of teaching experience and 11 years of research experience. He obtained his PhD from Anna University, Chennai in the year 2016. Machining, Manufacturing, and characterization of natural fibre reinforced composite materials are the areas of his interest and specialization. He has 41 journal publications in international reputed and 15 papers in international and national conferences. He written 5 books that were published by Lap Lambert, Technical publication and Krishna publication.

Lenin Nagarajan is a Professor of the Mechanical Engineering Department, Vel Tech Rangarajan Dr. Sagunthala R&D Institute of Science and Technology. He is having 18 years of teaching experience and 15 years of research experience. He obtained his PhD from Anna University, Chennai in the year 2015. Manufacturing optimization, facility layout design, selective assembly and machinability studies on composite materials are the areas of his interest and specialization. He has 54 journal publications in international reputed and 30 papers in international and national conferences. He organized 4 international conferences and 6 national conferences. He edited 2 books that were published by Springer and Lap Lambert.

Kalpathi Mathivanan is working as a Professor in Department of Mechanical Engineering at SV College of Engineering, Tirupati, Andra Pradesh, India. He obtained his PhD from Anna University, Chennai in the year 2018. He is having 17 years of teaching and 8 years of research experience. His areas of research interest include friction stir welding, Tribological characterization, and manufacturing optimization. He published 14 papers in international peer-reviewed journals and presented around 21 papers in international and national conferences.

Thomas Manvel Raj is a Professor in Department of Mechanical Engineering in Dhanalakshmi Srinivasan College of Engineering and Technology. He is having 27 years of teaching as well as research experience. His areas of research interest include micro machining, Tribological characterization of nano materials, optimization and polymer composite materials. He has more than 60 journal publications in international reputed journals and 40 papers in international and national conferences.